


Crystal structure of lutetium disilicate, $\text{Lu}_2\text{Si}_2\text{O}_7$

F. Soetebier and W. Urland*

Universität Hannover, Institut für Anorganische Chemie, Callinstr. 9, D-30167 Hannover, Germany

Received November 26, 2001, accepted February 5, 2002; CSD-No. 412249

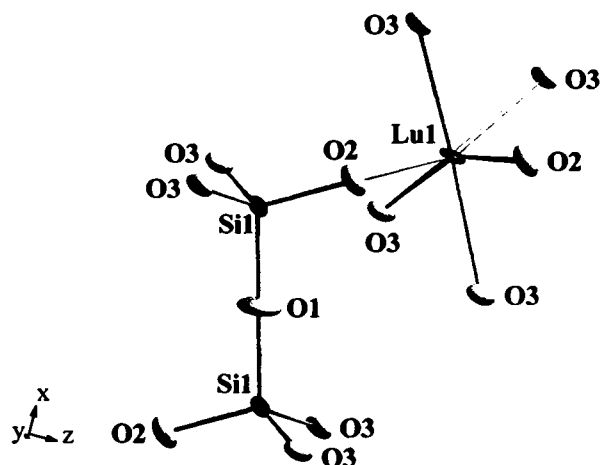

centre of symmetry. If there was a deviation of this angle, the thermal displacement ellipsoid should be larger. The terminal oxygen atoms of the disilicate group show a staggered confirmation (cf. figure).

Table 1. Data collection and handling.

Crystal:	colorless rod-like, size 0.026 × 0.056 × 0.185 mm
Wavelength:	Mo $K\alpha$ radiation (0.71073 Å)
μ :	180.34 cm ⁻¹
Diffractometer, scan mode:	Stoe IPDS, 240 exposures, $\Delta\varphi = 1.2^\circ$
$2\theta_{\text{max}}$:	56.1°
$N(hkl)_{\text{measured}}$, $N(hkl)_{\text{unique}}$:	2823, 331
Criterion for I_{obs} , $N(hkl)_{\text{gt}}$:	$I_{\text{obs}} > 2\sigma(I_{\text{obs}})$, 311
$N(\text{param})_{\text{refined}}$:	32
Programs:	SHELXS-97 [2], SHELXL-97 [3]

Abstract

$\text{Lu}_2\text{O}_7\text{Si}_2$, monoclinic, $C12/m1$ (No. 12), $a = 6.762(2)$ Å, $b = 8.835(3)$ Å, $c = 4.711(2)$ Å, $\beta = 101.99(4)^\circ$, $V = 275.3$ Å³, $Z = 2$, $R_{\text{gt}}(F) = 0.019$, $wR_{\text{ref}}(F^2) = 0.045$, $T = 293$ K.

Source of material

In attempt to prepare Lu^{3+} - β'' -alumina by ion exchange reaction of Na^+ - β'' - Al_2O_3 with LuCl_3 in a quartz tube under argon atmosphere we obtained crystals of $\text{Lu}_2\text{Si}_2\text{O}_7$. Lutetium disilicate was grown as colourless rod-like crystals from the LuCl_3 melt (Aldrich 99.99%) via reaction with SiO_2 of the tube after heating at 1223 K for 23 hours.

Discussion

$\text{Lu}_2\text{Si}_2\text{O}_7$ isotypically to thortveitite, as already derived from powder investigations and film methods on single crystals [1]. The crystal structure parameters (e.g. atomic sites, displacement parameters and distances) have been determined and refined on single crystals for the first time. The Si—O distances vary from 161 to 163 pm, the Lu—O distances range from 220 to 226 pm. The Si—O—Si angle of 180° in the Si_2O_7 group is forced by the

References

1. Felsche, J.: Polymorphism and crystal data of the rare-earth disilicates of the type $\text{RE}_2\text{Si}_2\text{O}_7$. *J. Less-Common Met.* **21** (1970) 1–14.
2. Sheldrick, G. M.: SHELXS-97, a program for the solution of crystal structures. University of Göttingen, Germany 1997.
3. Sheldrick, G. M.: SHELXL-97, a program for crystal structure refinement. University of Göttingen, Germany 1997.

Table 2. Atomic coordinates and displacement parameters (in Å²).

Atom	Site	x	y	z	U_{11}	U_{22}	U_{33}	U_{12}	U_{13}	U_{23}
Lu(1)	4h	1/2	0.80718(4)	0	0.0011(2)	0.0041(2)	0.0064(3)	0	0.0003(1)	0
Si(1)	4i	0.7196(3)	1/2	0.4121(6)	0.003(1)	0.005(1)	0.004(1)	0	−0.0005(8)	0
O(1)	2c	1/2	1/2	1/2	0.004(2)	0.024(5)	0.017(6)	0	0.005(4)	0
O(2)	4i	0.8832(9)	1/2	0.716(2)	0.005(3)	0.007(3)	0.007(3)	0	−0.002(2)	0
O(3)	8j	0.7367(6)	0.6510(5)	0.220(1)	0.003(2)	0.006(2)	0.007(3)	0.001(2)	0.000(2)	0.003(2)

* Correspondence author (e-mail: urland@acc.uni-hannover.de)